

EVERLAM™ SUPER TOUGH

EXTRA STRENGTH FOR LAMINATED SAFETY GLASS

CONTENTS

EXTRA STRENGTH FOR LAMINATED SAFETY GLASS 1

OFFERING 1

TYPICAL PROPERTIES 2

APPLICATIONS 2

RHEOLOGICAL PROPERTIES 3

COMPLIANCE WITH NATIONAL STANDARDS 4

POINTS OF INTEREST:

- Higher Young modulus
- Intended for structural applications
- Roll form, refrigerated and interleaved
- Special rheology
- Compliance with national standards for balustrades and canopies

Everlam N.V. is a 25 year-experienced company in PVB manufacturing, whose factory is placed in Uentrop, Germany.


Everlam™ Super Tough is a PVB-based solution which is intended for applications where higher Young modulus is requested so that laminated safety glass can stand upright longer after breakage, which enhances the protection for people and objects.

From structural design point of view, the special rheology of this interlayer allows to design thinner glass to get the same mechanical performance as for standard laminates, which can lead to glazing weight reduction

Everlam™ Super Tough can be laminated with a standard lamination line and typical autoclave

cycle as for other Everlam™ PVB grades, meaning no need for any additional investment in machinery. As well as with fully tempered and heat strengthened glass, it can also be laminated with PLF panels, which makes it ideal to produce structural glazing with a high yield performance in a lamination line.

Everlam™ Super Tough meets architectural safety standards like EN356, EN 12543, EN12600, ANSI Z97.1-2015 and CPSC 16 CFR 1201, together with national standards applicable for balustrade and canopy glazing.

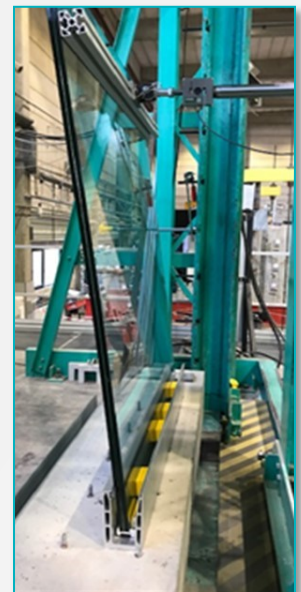

OFFERING

Everlam™ Super Tough structural interlayer is supplied in roll form, refrigerated and interleaved.


Item	Feature
Product code	LAM72T
Color	Clear
Thickness (mm)	0.76
Width range (cm)	100-321
Available SKU's (cm)	100, 120, 130, 160, 225, 260 and 321

TYPICAL PROPERTIES

Group	Property	Test method	Units	Test conditions	Typical value
Physical	Specific gravity	ASTM D792	-	23 °C	1.081
	Moisture content	NIR	%	-	0.45
Mechanical	Tensile strength	EN ISO 527	MPa	24 °C/30% RH	36.1
	Elongation at break	EN ISO 527	%	24 °C/30% RH	198
Optical	Light transmission	EN410	%	-	>88
	UV transmission	ISO 9050	%	-	<2
	Haze	ASTM D1003	%	-	0.2
Thermal	Melt flow rate	ISO 1133:2005	g/10 cm	150 °C/5Kg	0.41
	Glass transition temperature (T _g)	DMA	°C	1 Hz at 3 °C/min Maximum phase angle	45
	Heat of combustion	ISO 1716	MJ/Kg	-	29.84
	Thermal expansion coefficient	ASTM E831	10 ⁻⁶ /°C	5 °C-110 °C	233
	Thermal conductivity	ASTM D5930	W/m °K	35 °C	0.33

APPLICATIONS

Thanks to its specific rheology, Everlam™ Super Tough can be the product of choice for the following applications:

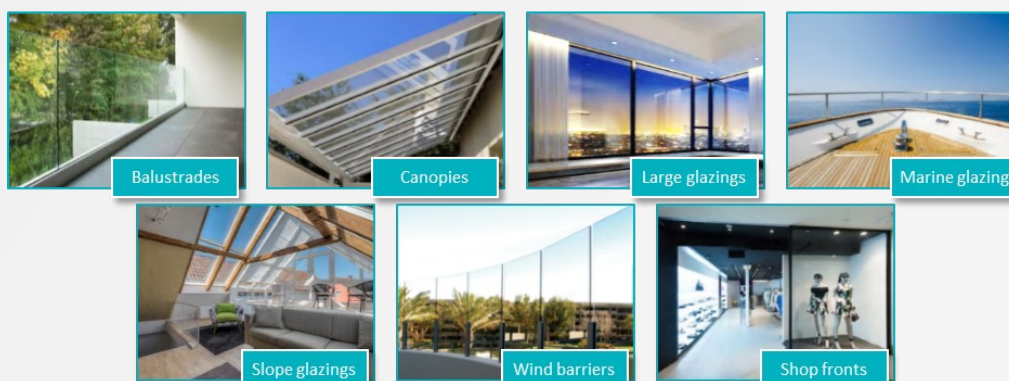

STRUCTURAL INTERLAYER

RHEOLOGICAL PROPERTIES

Everlam™ Super Tough is a high modulus PVB solution which has been developed to present enhanced mechanical performance for structural application thanks to its special rheological properties, a shown in tables below:

Load Duration	EVERLAM™ SUPER TOUGH (LAM72T) Young Modulus E' (Mpa)														
	Temperature														
	15 (°C)	20 (°C)	25 (°C)	30 (°C)	33 (°C)	36 (°C)	40 (°C)	43 (°C)	46 (°C)	50 (°C)	53 (°C)	56 (°C)	60 (°C)	65 (°C)	70 (°C)
1 sec	436.25	369.51	284.60	179.09	136.22	77.31	31.02	12.96	5.26	3.09	1.86	1.41	1.29	1.44	1.37
3 sec	406.81	333.05	242.31	130.88	90.72	43.58	13.01	5.66	2.67	1.85	1.38	1.29	1.25	1.32	1.25
30sec	335.63	249.59	143.66	52.62	25.68	8.58	2.98	1.77	1.38	1.34	1.22	1.14	1.01	1.09	1.01
1 min	314.68	231.64	113.39	33.04	15.98	5.26	2.19	1.45	1.29	1.28	1.17	1.05	0.95	0.98	1.01
5 min	238.01	159.32	55.99	10.54	4.79	2.37	1.38	1.26	1.22	1.11	0.98	0.88	-	-	-
10 min	227.94	129.01	37.08	6.37	3.07	1.65	1.32	1.28	1.14	1.05	0.92	-	-	-	-
30 min	185.16	87.65	17.18	3.07	1.96	1.38	1.28	1.17	1.09	0.92	-	-	-	-	-
1 hour	159.32	60.62	10.53	2.30	1.50	1.44	1.22	1.08	0.95	-	-	-	-	-	-
6 hours	80.05	21.29	3.17	1.38	1.26	1.20	1.01	0.88	-	-	-	-	-	-	-
12 hours	57.59	11.96	2.29	1.32	1.28	1.14	0.95	-	-	-	-	-	-	-	-
1 day	37.08	7.21	1.77	1.38	1.22	1.13	-	-	-	-	-	-	-	-	-
5 days	12.96	2.67	1.32	1.17	1.05	0.88	-	-	-	-	-	-	-	-	-
1 week	9.67	2.30	1.29	1.14	1.01	-	-	-	-	-	-	-	-	-	-
3 weeks	4.76	1.50	1.25	1.01	0.88	-	-	-	-	-	-	-	-	-	-
1 month	3.67	1.42	1.22	0.98	-	-	-	-	-	-	-	-	-	-	-
1 year	1.41	1.25	0.95	-	-	-	-	-	-	-	-	-	-	-	-
10 years	1.25	1.01	-	-	-	-	-	-	-	-	-	-	-	-	-
15 years	1.22	0.95	-	-	-	-	-	-	-	-	-	-	-	-	-
50 years	1.08	-	-	-	-	-	-	-	-	-	-	-	-	-	-

Load Duration	EVERLAM™ SUPER TOUGH (LAM72T) Shear Modulus G' (Mpa)														
	Temperature														
	15 (°C)	20 (°C)	25 (°C)	30 (°C)	33 (°C)	36 (°C)	40 (°C)	43 (°C)	46 (°C)	50 (°C)	53 (°C)	56 (°C)	60 (°C)	65 (°C)	70 (°C)
1 sec	146.39	124.00	95.50	60.10	45.71	25.94	10.41	4.35	1.77	1.04	0.62	0.47	0.43	0.48	0.46
3 sec	136.51	111.76	81.31	43.92	30.44	14.62	4.37	1.90	0.90	0.62	0.46	0.43	0.42	0.44	0.42
30 sec	112.63	83.76	48.21	17.66	8.62	2.88	1.00	0.59	0.46	0.45	0.41	0.38	0.34	0.37	0.34
1 min	105.60	77.73	38.05	11.09	5.36	1.77	0.74	0.49	0.43	0.43	0.39	0.35	0.32	0.33	0.34
5 min	79.87	53.46	18.79	3.54	1.61	0.79	0.46	0.42	0.41	0.37	0.33	0.30	-	-	-
10 min	76.49	43.39	12.44	2.14	1.03	0.55	0.44	0.43	0.38	0.35	0.31	-	-	-	-
30 min	62.13	29.41	5.77	1.03	0.66	0.46	0.43	0.39	0.37	0.31	-	-	-	-	-
1 hour	53.46	20.34	3.53	0.77	0.50	0.48	0.41	0.36	0.32	-	-	-	-	-	-
6 hours	26.86	7.14	1.06	0.46	0.42	0.40	0.34	0.30	-	-	-	-	-	-	-
12 hours	19.33	4.01	0.77	0.44	0.43	0.38	0.32	-	-	-	-	-	-	-	-
1 day	12.44	2.42	0.59	0.46	0.41	0.38	-	-	-	-	-	-	-	-	-
5 days	4.35	0.90	0.44	0.39	0.35	0.30	-	-	-	-	-	-	-	-	-
1 week	3.24	0.77	0.43	0.38	0.34	-	-	-	-	-	-	-	-	-	-
3 weeks	1.60	0.50	0.42	0.34	0.30	-	-	-	-	-	-	-	-	-	-
1 month	1.23	0.48	0.41	0.33	-	-	-	-	-	-	-	-	-	-	-
1 year	0.47	0.42	0.32	-	-	-	-	-	-	-	-	-	-	-	-
10 years	0.42	0.34	-	-	-	-	-	-	-	-	-	-	-	-	-
15 years	0.41	0.32	-	-	-	-	-	-	-	-	-	-	-	-	-
50 years	0.36	-	-	-	-	-	-	-	-	-	-	-	-	-	-

COMPLIANCE WITH NATIONAL STANDARDS

NBN B03-004:2017 BELGIUM

The purpose of this standard is to check the capability of the balustrade to resist forces applied normally or by accident by one or several users.

The loads applied to rank the system performance are:

- Service load.
- Security load
- Limit service
- Last service
- Soft body impact

Everlam™ Super Tough laminates have successfully been tested to be fit for use in residential areas, offices, restaurants, cinemas theaters, dancing halls, gyms, shops...

CTE SPAIN

The Spanish Technical Building Code (Código Técnico de la Edificación) is compulsory in that country. This document ranks the balustrade system resistance category in function on the installation area.

The system is submitted to:

- Static charge.
- Impact: soft and hard body.

Everlam™ Super Tough laminates are able to withstand a linear load of 3KN/m, allowing them to be fit for use in crowded areas.

EVERLAM N.V

Everlam N.V.
Blockhuisstraat, 47J.
2800 Mechelen.
Belgium.
Phone: +32 (0) 15 48 08 00
Email: info@Everlam.com

UNI 11678 ITALY

This standard defines the test methods to determine the performance of anti-fall glass versus static linear and dynamic loads.

The system is ranked according to performance for:

- Linear static load test.
- Impact test: hard body and soft body.

Everlam™ Super Tough laminates have successfully been tested up to a linear load of 2 KN/m for slab and floor mounted systems.

EOTA, EAD- 220025-00-0401 AND EOTA, TR001 FOR CANOPY TESTING

The mechanical performance requested for this application is described in the European Assessment document issued by the European Organization for Technical Assessment.

The system is evaluated according to:

- Snow load mechanical resistance.
- Impact: soft and hard body.
- Residual load capacity.

Everlam™ Super Tough laminates did not fail either hard body or soft body impact or residual load tests.

DIN 18008: 2020-5 GERMANY

Laminates made with Everlam™ Super Tough interlayer fulfill impact test categories:

- P1A.
- 1B1.